




# Report Test

## LowTemperatureCheck

Identification		Identification		ISO 2921 - Temperature	
Job :	(Generic)	Product :	Compound 01	Conditioning Time	10 min
Order:	test cal	Product Code :		Immersion temperature	-70 °C
Lot :	cal	Treatment :		Test Start Temperature	-65 °C
		Customer :	Customer 01	Final Temperatura	0 °C
		Customer Code :		Temperature Gradient	1 °C
Data :	20/12/2005	Operatore :	Administrator		

Notes : ShoreA Hardness  
IRHD Hardness  
Density [g/cm3]

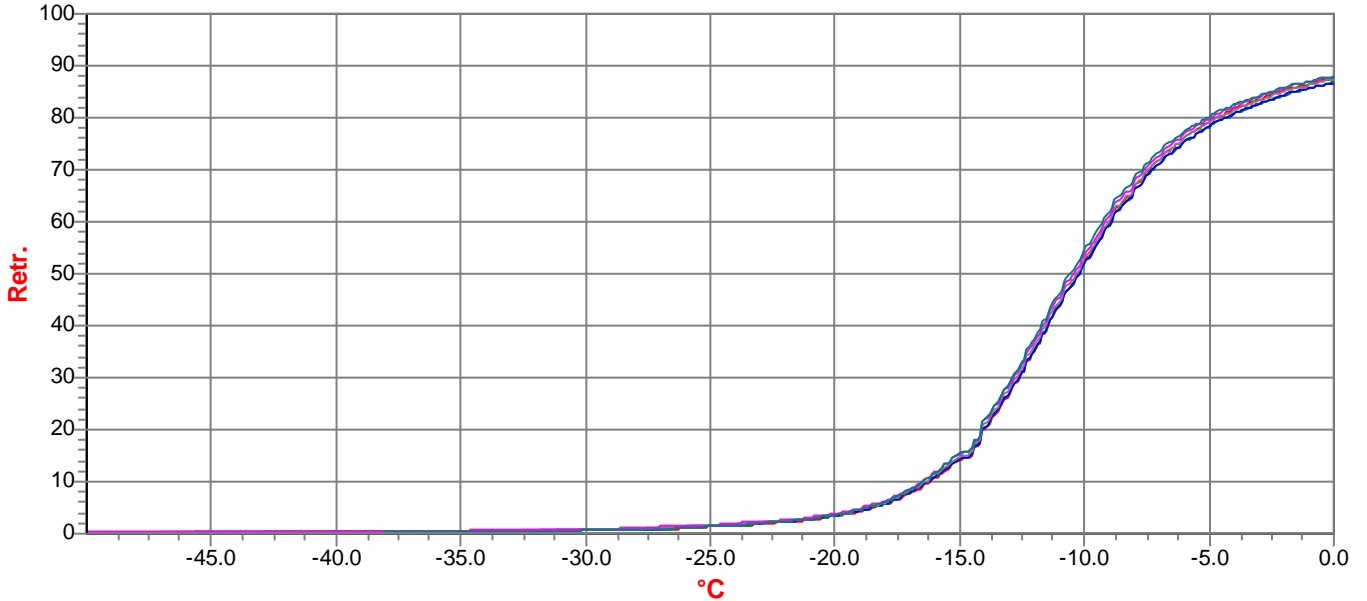

Batch/NSam	TR 10 °C	TR 30 °C	TR 50 °C	TR 70 °C	DTR 10-70 °C	t 10 min	t 30 min	t 50 min	t 70 min
<b>Max Tol</b>	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00
<b>Min Tol</b>	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00
<span style="color: red;">■</span> 1/1	-16.20	-12.70	-10.30	-7.50	8.70	48.26	51.73	54.14	57.03
<span style="color: green;">■</span> 1/2	-16.30	-12.70	-10.20	-7.30	9.00	48.17	51.70	54.19	57.17
<span style="color: blue;">■</span> 1/3	-16.30	-12.70	-10.30	-7.40	8.90	48.17	51.70	54.18	57.16
<span style="color: grey;">■</span> 1/4	-16.40	-12.80	-10.30	-7.50	8.90	48.05	51.60	54.09	56.98
<span style="color: magenta;">■</span> 1/5	-16.50	-12.90	-10.40	-7.60	8.90	47.96	51.52	53.97	56.84
<span style="color: cyan;">■</span> 1/6	-16.50	-12.90	-10.60	-7.70	8.80	47.97	51.47	53.87	56.71
<b>Max</b>	0.00	0.00	0.00	0.00	9.00	48.26	51.73	54.19	57.17
<b>Min</b>	-16.50	-12.90	-10.60	-7.70	8.70	47.96	51.47	53.87	56.71
<b>Ave</b>	-16.37	-12.78	-10.35	-7.50	8.87	48.10	51.62	54.07	56.98
<b>St.dev</b>	0.1211	0.0983	0.1378	0.1414	0.1033	0.1219	0.1075	0.1279	0.1808
<b>Cp</b>	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00
<b>Cpk</b>	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00

Signature \_\_\_\_\_





# Report Test

## Brittleness Point Test

Identification	Identification	Brittleness Point Standard
<b>Job :</b> (Generic) <b>Order :</b> Order 001 <b>Lot :</b> Lot 001 <b>Batch :</b> 1  <b>Date :</b> 22/08/2005	<b>Product :</b> Compound 01 <b>Product Code :</b> 001 <b>Treatment :</b> Original State <b>Customer :</b> Customer 01 <b>Customer Code :</b> Cus001 <b>Operator :</b> Administrator	<b>Conditioning Time</b> 3 min <b>Type of Sample (1=A, 2=B)</b> 1

**Notes :**

<b>N° Test</b>	<b>Bpt</b>	
	°C	
<b>Max Tol.</b>	0.00	
<b>Min Tol.</b>	0.00	
	-44.00	

Test Details												
N°	Degr.	m/sec	P1	P2	P3	P4	P5	P6	P7	P8	P9	P10
1	-53.3		ok	ok	ok	brocken	brocken	brocken	ok	ok	ok	cracked
2	-44.1		ok	ok	ok	ok	ok	ok	ok	ok	ok	ok
3	-46.6		ok	ok	cracked	ok	ok	ok	ok	cracked	ok	ok

**Signature** \_\_\_\_\_

